

Control of Electrons' Spin Eliminates Hydrogen Peroxide Formation During Water Splitting

Document Version:

Accepted author manuscript (peer-reviewed)

Citation for published version:

Mtangi, W, Tassinari, F, Vankayala, K, Jentzsch, AV, Adelizzi, B, Palmans, ARA, Fontanesi, C, Meijer, EW & Naaman, R 2017, 'Control of Electrons' Spin Eliminates Hydrogen Peroxide Formation During Water Splitting', *Journal of the American Chemical Society*, vol. 139, no. 7, pp. 2794-2798. https://doi.org/10.1021/jacs.6b12971

Total number of authors:

9

Digital Object Identifier (DOI):

10.1021/jacs.6b12971

Published In:

Journal of the American Chemical Society

License:

Unspecified

General rights

@ 2020 This manuscript version is made available under the above license via The Weizmann Institute of Science Open Access Collection is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognize and abide by the legal requirements associated with these rights.

How does open access to this work benefit you?

Let us know @ library@weizmann.ac.il

Take down policy

The Weizmann Institute of Science has made every reasonable effort to ensure that Weizmann Institute of Science content complies with copyright restrictions. If you believe that the public display of this file breaches copyright please contact library@weizmann.ac.il providing details, and we will remove access to the work immediately and investigate your claim.



Article

pubs.acs.org/JACS

¹ Control of Electrons' Spin Eliminates Hydrogen Peroxide Formation ² During Water Splitting

- ³ Wilbert Mtangi,[†] Francesco Tassinari,[†] Kiran Vankayala,[†] Andreas Vargas Jentzsch,[‡]
 ⁶ Beatrice Adelizzi,[‡]
 ⁴ Anja R. A. Palmans,[‡] Claudio Fontanesi,[§] E. W. Meijer,^{*,‡}
 ⁶ and Ron Naaman^{*,†}
- 5 [†]Department of Chemical Physics, Weizmann Institute of Science, Rehovot 76100, Israel
- 6 [‡]Institute for Complex Molecular Systems, Eindhoven University of Technology, 5600 MB Eindhoven, The Netherlands
- ⁷ Department of Engineering, University of Modena and Reggio Emilia, Via Vivarelli 10, 41125 Modena, Italy
- 8 Supporting Information

10

11

12

13

14

15

16 17

18


19

20

2.1

22

ABSTRACT: The production of hydrogen through water splitting in a photoelectrochemical cell suffers from an overpotential that limits the efficiencies. In addition, hydrogen-peroxide formation is identified as a competing process affecting the oxidative stability of photoelectrodes. We impose spin-selectivity by coating the anode with chiral organic semiconductors from helically aggregated dyes as sensitizers; Zn-porphyrins and triarylamines. Hydrogen peroxide formation is dramatically suppressed, while the overall current through the cell, correlating with the water splitting process, is enhanced. Evidence for a strong spin-selection in the chiral semiconductors is presented by magnetic conducting (mc-)AFM measurements, in which chiral and achiral Zn-porphyrins are compared. These findings contribute to our

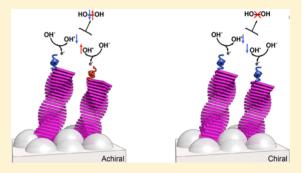

understanding of the underlying mechanism of spin selectivity in multiple electron-transfer reactions and pave the way toward better chiral dye-sensitized photoelectrochemical cells.

23 INTRODUCTION

24 Since it has no carbon, has the highest specific enthalpy of 25 combustion of any chemical fuel, and generates water as its 26 oxidation product, hydrogen has been referred to as the fuel of 27 the future. Although significant progress has been made over 28 the past decades,² the generation of hydrogen by green, 29 sustainable methods on a global scale remains a future goal.^{3–8} 30 While technologies exist for the electrolysis of water and 31 photoelectrochemical generation of hydrogen from water, the 32 processes involve significant overpotentials and the formation 33 of peroxides and superoxide radical byproducts. These 34 byproducts have the tendency to adsorb onto the photocatalyst, 35 poisoning it, thereby reducing its stability and lifetime. 10 36 Although specific catalysts are proposed to use the peroxides as 37 intermediates, 11 this path requires higher voltage. Therefore, a fundamental solution for the off-pathway products is essential. Water splitting is a four-electron process that generates 40 hydrogen molecules having singlet ground states and oxygen 41 molecules having triplet ground states. Commonly, the artificial 42 water splitting process requires an overpotential of about 0.6 V 43 vs normal hydrogen electrode (NHE), to drive the oxygen 44 evolution reaction. 12-14 The importance of electron-spin 45 correlation of electrons in generating O2 has been debated 46 for biological photosynthesis. Particularly the chemistry 47 associated with the oxygen evolution reaction in photosystem 48 II has been examined. 15-17 Nevertheless, the details of the 49 mechanism of the O=O bond formation remain unresolved. ^{18–20} Although the spin state of the electrons involved 50 is rarely discussed in works exploring artificial photosynthesis, 51 recent theoretical studies suggest that the overpotential 52 required to split water is linked to restrictions on the electrons' 53 spin in generating a ground state triplet oxygen molecule. ^{21,22} 54 In recent experimental work, it has been shown that when the 55 anode in the water splitting cell is coated with chiral molecules, 56 the overpotential is reduced. ²³ It has been proposed that the 57 effect is due to spin filtering occurring when electrons are 58 conducted through chiral systems. ²⁴ However, and very 59 importantly, the possible role of the spin control in suppressing 60 the formation of hydrogen peroxide has not been discussed nor 61 experimentally addressed.

Here, we hypothesize that hydrogen peroxide is produced 63 due to uncontrolled spin alignment²⁵ and greatly contributes to 64 the high overpotentials. Hence, controlling the spin state of the 65 electronic potential on which the reaction occurs should result 66 in more efficient oxygen production and limited production of 67 hydrogen peroxide. Although we do not strive here to present 68 the highest production of hydrogen and oxygen—optimizing the 69 cells is ongoing—the results presented show an unprecedented 70 control of chemical kinetics through spin selection.

Received: December 17, 2016 Published: January 30, 2017



72 RESULTS AND DISCUSSION

f1

73 To first control the spin state, the ITO anode in the 74 photoelectrochemical cell was coated with two families of 75 organic semiconductors, Zn porphyrins and tri(pyrid-2-yl)-76 amine trisamide, TPyA, both in their chiral (using enantiomeri-77 cally pure side chains) and achiral (using achiral side chains) 78 versions (Figure 1A,B). By modifying the side chains of the

Α (S-TPyA) (a.u.) Absorbance 400 500 350 400 Wavelength (nm) Wavelength (nm) 40 CD (mdeg) 20 00 -25 Wavelength (nm) Wavelength (nm)

Figure 1. Molecules used as photosensitizer and their supramolecular aggregation. (A) The chiral and achiral Zn porphyrins, (C and E) their absorption spectra and CD spectra of the aggregated state in solution $(1.7 \times 10^{-5} \text{ M} \text{ in methylcyclohexane})$ and when adsorbed on the surface (inset) (B) the chiral and achiral TPyA, (D and F) their absorption and CD spectra of the aggregated state in solution and when adsorbed on the surface (inset). The red curves represent the chiral molecules, while the blue represent the achiral ones.

79 molecules, we control the resulting helical supramolecular 80 assemblies into either a bias for one helical sense or a racemic 81 mixture of both helical senses, respectively. Thus, in the present 82 study, electrons are transmitted into the TiO₂ substrate through 83 the same molecular system, which only differs in its molecular 84 organization; either one helical sense or a mixture of both. In 85 the case of Zn-porphyrins, the 390 nm Soret band confirms the 86 formation of helical supramolecular structures in solution 87 (Figure 1C), ^{26,27} which are retained when transferred to the 88 surface (inset of Figure 1C). In a similar manner, the 317 nm 89 band is indicative of the formation of a supramolecular 90 assembly for the TPyA molecules. For both molecules, the 91 chiral analogues show a strong CD response which is not 92 observed in the achiral version (Figure 1E,F). The achiral 93 molecules most probably aggregate in equal amounts of left-

and right-handed helices (racemic mixture), while the chiral 94 molecules prefer one of both only.

Magnetic conducting atomic force microscopy (mc-AFM) 96 measurements were conducted to verify the spin selectivity of 97 electron transmission through the Zn-porphyrin stacks. 28 98 Figure 2B shows the dependence of the current on the 99 f2

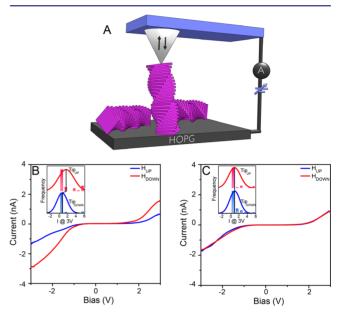


Figure 2. Magnetic conducting atomic force microscopy (mc-AFM) measurements on stacks of chiral and achiral Zn-porphyrins. (A) The experimental setup. The current as a function of the applied voltage obtained from the chiral (B) and achiral (C) Zn-porphyrin molecules. The insets show corresponding histograms of currents obtained at 3 V for the two opposite magnetic orientations of the tip.

orientation of the magnetic field at the tip of the mc-AFM for 100 the stack of chiral porphyrins, which confirms that one spin is 101 preferred over the other. It is important to realize that the ratio 102 between the two spin currents is affected by the nonideal spin 103 injection from the magnetic tip. Since the spin polarization of 104 the tip is only about 35%, it means that the actual spin filtering 105 of the molecular system is about 4:1, in other words only about 106 20% of the electrons conducted through the chiral molecular 107 aggregates in this experiment have the "wrong" spin. From 108 Figure 2C, it can be observed that for the achiral compounds, 109 the magnitude of the current measured as a function of applied 110 bias does not depend on the orientation of the magnetic field; 111 hence the conduction through this system with equal amount 112 of right and left handed helices is not spin specific. These 113 results indicate that the supramolecular structures formed from 114 the chiral porphyrins can efficiently filter spins and are 115 consistent with previous reports in which chiral molecules 116 have been observed to be good spin filters.²⁵

Next, photoelectrochemical measurements were conducted 118 in a three-electrode cell, with the Ag/AgCl (saturated KCl) as 119 the reference electrode and a Pt wire as the cathode (Figure 3). 120 f3 A 0.1 M Na_2SO_4 (pH = 6.56) aqueous solution was used as the 121 electrolyte. TiO_2 substrates fabricated and functionalized as 122 outlined in the Supporting Information, were used as 123 photoanodes. In these cells, the magnitude of the measured 124 current is correlated with the amount of oxygen bubbles 125 produced at the anode and hydrogen bubbles at the cathode. 23 126 Higher photography densities are observed for photography.

Higher photocurrent densities are observed for photo- 127 electrodes functionalized with helical aggregates of chiral 128

Journal of the American Chemical Society

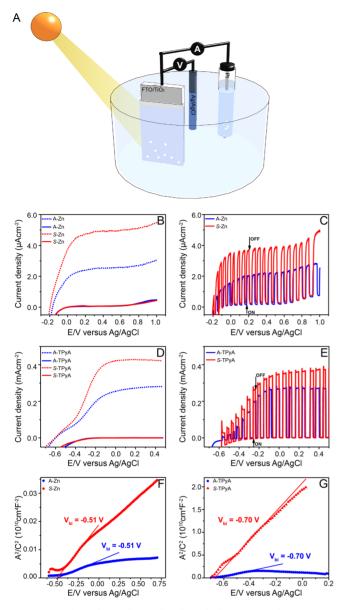


Figure 3. Photoelectrochemical cell and the current density as a function of the potential. In A, a schematic representation of the photoelectochemical cell. The potential is given vs the Ag/AgCl electrode, when the TiO₂ electrode is coated with self-assembled achiral (blue lines) or chiral (red lines) molecules. In (B) and (C), Zn-porphyrins were used while in (D) and (E), TPyA molecules were employed. The measurements were performed in the dark (solid lines) and under illumination (dotted lines). In (C) and (E) measurements were performed while chopping the light. All measurements were performed at a scan rate of 10 mVs⁻¹. The flat-band potentials in the dark for Zn-porphyrin and TPyA molecules were obtained from Mott—Schottky plots (F and G, respectively) at a frequency of 1.99 kHz and oscillation voltage of 20 mV.

129 molecules with preferred helicity, compared to those coated 130 with racemic aggregates of achiral ones. This is remarkable, 131 given that the chemical compositions of the chiral and achiral 132 molecules for the two sets used in this study are very similar, 133 except for the stereocenter present in the chiral molecules. In 134 general, the magnitude of the photocurrents obtained with the 135 Zn-porphyrins are typically low, as has also been observed by 136 Moore et al. 30 With the TPyA molecules, the photocurrent 137 densities are reasonably high, since UV light is used for

illumination of the cell. The activity of the photoelectrodes is 138 known to depend strongly on their electronic properties, 139 therefore Mott–Schottky measurements were performed to 140 characterize the electronic properties of ${\rm TiO_2}$ electrodes 141 modified with aggregates of Zn porphyrin and TPyA molecules. 142 A flat-band potential, $V_{\rm bi}$ of $-0.51~{\rm V}$ vs Ag/AgCl was obtained 143 in the dark for both the chiral and the achiral Zn-porphyrins 144 (Figure 3E), while a value of approximately $-0.70~{\rm V}$ vs Ag/ 145 AgCl was obtained for the TPyA molecules (Figure 3F), an 146 indication that the difference in the photocurrents, for chiral 147 and achiral species, is not related to the modification of the 148 electronic properties of the photoelectrodes. Thus, the 149 differences in the photocurrents must be attributed to the 150 chirality of the molecules.

After showing the difference in water splitting for the chiral 152 versus racemic aggregates, the beneficial effect of electrons' spin 153 control is highlighted by its effect on hydrogen peroxide 154 formation. An indirect quantification of the H_2O_2 produced 155 during photoelectrochemical water splitting was conducted. 156 Spectrophotometric titration of the used electrolytes were 157 performed using 0-tolidine as redox indicator. The amount 158 of peroxide formed has been quantified through Ellms-Hauser 159 method calibrating the system with commercial H_2O_2 (see 160 Figures S12–S14). In the presence of H_2O_2 , a yellow color 161 appears with an absorption peak at about 436 nm. This peak is 162 characteristic for the complete two-electron oxidation product 163 of 0-tolidine formed by the reaction with hydrogen peroxide. 33 164

The electrolyte obtained from the bare TiO2 and electrodes 165 functionalized with achiral dyes showed the characteristic peak 166 at 436 nm, indicating the production of H₂O₂ during water 167 oxidation (see Table S1). Fascinatingly, no detectable amount 168 of hydrogen peroxide was observed for electrodes with the 169 chiral molecules physisorbed (Figure 4A,B). Noticeably, after 170 f4 40 min of irradiation, $43 \pm 5 \text{ mmol}\text{L}^{-1}$ of hydrogen peroxide 171 have been produced with the achiral Zn-porphyrin function- 172 alized system while nondetectable levels of peroxide have been 173 found using the chiral analogue. The TPyA functionalized 174 systems show low absorbance intensity at 436 nm. The 175 relatively low level of H2O2 in the case of A-TPyA may result 176 for performing the electrochemistry measurements under 177 illumination with UV light, which might have led to the 178 disproportionation of the produced peroxide before titration. 179 However, also in this case, much less H₂O₂ is produced with 180 the chiral molecules (S-TPyA) than with the achiral ones (A- 181 TPyA). Additional evidence is obtained by using achiral 3- 182 mercaptopropionic acid and the chiral oligopeptide [(COO- 183 H)— $(Ala-Aib)_7$ —NH— $(CH_2)_2$ —SH] (see Figure S13). Only 184 the latter decreases the H₂O₂ production. These results further 185 indicate that the observed elimination of the hydrogen peroxide 186 production is general for all chiral molecules.

The results presented here in the quantification of H_2O_2 188 production together with the electrochemistry data show a 189 strong correlation between the overpotential, the formation of 190 H_2O_2 , and the electron's spin alignment control. During water 191 splitting, two OH^- species must combine to form molecular 192 oxygen in its triplet ground state. In the process, an electron 193 from each OH^- is transferred to the anode. This leaves the two 194 OH^{\bullet} radicals in their doublet ground state, namely each OH^{\bullet} 195 has one unpaired electron. When there is no spin control and 196 the interaction electronic potential has a singlet character, the 197 formation of H_2O_2 is possible (Figure 4). However, when the 198 electron's spins are aligned in a parallel fashion, the two 199 electrons interact on the triplet potential surface which 200

Journal of the American Chemical Society

242

243

260

269

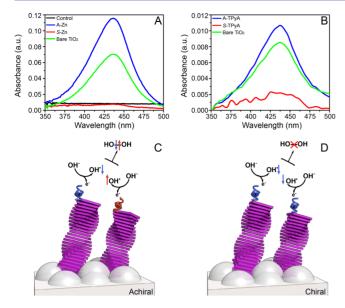


Figure 4. Control of the hydrogen peroxide production. UV-vis absorption spectra from the titration of the used electrolyte (Na₂SO₄) with o-tolidine of bare TiO2 and TiO2 electrodes coated with (A) selfassembled Zn-porphyrins of either achiral (A-Zn) or chiral (S-Zn) and (B) TPyA molecules. The control refers to the titration of unused Na₂SO₄ with o-tolidine. (C) When the electrons transfer to the anodes is non spin specific the spins of the unpaired electrons on the two OH^o are aligned antiparallel, hence the interaction between the two OH[•] is on a singlet surface that correlates with the production of hydrogen peroxide (H_2O_2) . (D) When the electron transfer to the anode is spin specific, the spins of the two electrons are aligned parallel to each other, hence the two OH interact on a triplet surface that forbids the formation of H2O2 and facilitates the production of oxygen in its ground state.

201 correlates with the formation of the ground state molecular 202 oxygen and on which the formation of H₂O₂ is symmetry

The formation of oxygen and hydrogen peroxide are 204 205 anticorrelated; i.e., the formation of one is coming at the 206 expense of the other. This is what the present results indicate. 207 However, it is difficult to draw a quantitative relation between the change in the current and the hydrogen peroxide formation, 209 since the change in the current reflects the change in the 210 threshold potential for the process while the decrease in the 211 hydrogen peroxide formation is an indication for the extent of 212 spin polarization. Of course, the substrate (the catalyst) may 213 induce spin-orbit coupling that will mix the spin states of the 214 OH radical. However, for TiO2 and other relatively light 215 materials, the spins of physisorbed molecules are expected to be 216 conserved, as observed by XPS studies.³⁴ Note that substrate-217 induced spin—orbit coupling may explain the low overpotential 218 observed for some oxides, 35,36 magnetic catalysts or catalysts 219 made from heavy atoms. For these systems, the side products 220 are not significantly suppressed. Indeed, no investigations were 221 performed in the past aimed at controlling the formation of 222 H_2O_2 .

223 CONCLUSIONS

224 The experimental results observed in the current study provide 225 new insights into the mechanism behind oxygen formation in 226 the oxygen evolution reaction and provide a new path for 227 improving the efficiency of the water splitting process. 228 Obviously, much work has to be done to optimize the system

with other and more effective chiral dyes, chiral semi- 229 conductors, and chiral catalysts, but a proof-of-principle to 230 make another counterintuitive approach is presented. The 231 control of electrons' spin in the chemical kinetics during the 232 photochemical water splitting will also rejuvenate the field of 233 magnetic field effects in chemical kinetics and related 234 phenomenon as reviewed by Steiner and Ulrich many years 235 ago, following the discovery and understanding of electron spin 236 polarized phenomena during chemical reactions. This is the 237 more of importance due to the recent interest in photoredox 238 catalysis in organic chemistry with exciting enatioselectivities. In 239 addition, the work points to the importance of chirality and 240 spin selectivity in multiple electron reactions in biology.

ASSOCIATED CONTENT

S Supporting Information

The Supporting Information is available free of charge on the 244 ACS Publications website at DOI: 10.1021/jacs.6b12971.

Experimental details, synthesis, preparation, and func- 246 tionalization of TiO2 electrodes. Additional details SEM, 247 spectroscopic data, photoelectrochemical measurements, 248 AFM mc-AFM, and spectrophotometric titration of 249 H_2O_2 (PDF)

■ AUTHOR INFORMATION	251
Corresponding Authors	252
*e.w.meijer@tue.nl	253
*ron.naaman@weizmann.ac.il	254
ORCID ®	255
Andreas Vargas Jentzsch: 0000-0003-1386-3174	256
E. W. Meijer: 0000-0003-4126-7492	257
Notes	258
The authors declare no competing financial interest.	259

ACKNOWLEDGMENTS

R.N. acknowledges discussion with Profs. Andrew Rapp and 261 David Waldeck and acknowledges partial support from the 262 European Research Council under the European Union's 263 Seventh Framework Program (FP7/2007-2013)/ERC grant 264 agreement no. [338720]. The Eindhoven laboratory acknowl- 265 edges financial support of EURO-SEQUENCES (H2020- 266 MSCA-ITN-2014, No 642083) and the FMS Gravitation 267 Program (No 024.001.035). 268

REFERENCES

- (1) Gray, H. B. Nat. Chem. 2009, 1 (1), 7. (2) Ager, J. W.; Shaner, M. R.; Walczak, K. A.; Sharp, I. D.; Ardo, S. 271 Energy Environ. Sci. 2015, 8 (10), 2811-2824. (3) Bard, A. J.; Fox, M. A. Acc. Chem. Res. 1995, 28 (3), 141-145. 273 (4) Blankenship, R. E.; Tiede, D. M.; Barber, J.; Brudvig, G. W.; 274 Fleming, G.; Ghirardi, M.; Gunner, M. R.; Junge, W.; Kramer, D. M.; 275 Melis, A.; Moore, T. A.; Moser, C. C.; Nocera, D. G.; Nozik, A. J.; Ort, 276 D. R.; Parson, W. W.; Prince, R. C.; Sayre, R. T. Science 2011, 332 277 (6031), 805-809. (5) Tachibana, Y.; Vayssieres, L.; Durrant, J. R. Nat. Photonics 2012, 6 279 (8), 511-518. (6) Reece, S. Y.; Hamel, J. A.; Sung, K.; Jarvi, T. D.; Esswein, A. J.; 281 Pijpers, J. J. H.; Nocera, D. G. Science 2011, 334 (6056), 645-648.
- (7) Han, Z.; Eisenberg, R. Acc. Chem. Res. 2014, 47 (8), 2537-2544. 283 (8) Yuhas, B. D.; Smeigh, A. L.; Douvalis, A. P.; Wasielewski, M. R.; 284 Kanatzidis, M. G. J. Am. Chem. Soc. 2012, 134 (25), 10353-10356. 285 (9) Fujishima, A.; Honda, K. Nature 1972, 238 (5358), 37–38.

- (10) Seabold, J. A.; Choi, K.-S. Chem. Mater. 2011, 23 (5), 1105-287 288 1112.
- (11) Kohl, S. W.: Weiner, L.: Schwartsburd, L.: Konstantinovski, L.: 2.89
- 290 Shimon, L. J. W.; Ben-David, Y.; Iron, M. A.; Milstein, D. Science 2009,
- 291 324 (5923), 74-77. 2.92
- (12) Sivula, K.; Le Formal, F.; Grätzel, M. ChemSusChem 2011, 4, 293 432-449.
- (13) Brillet, J.; Cornuz, M.; Formal, F. Le; Yum, J.-H.; Grätzel, M.; 294
- 295 Sivula, K. J. Mater. Res. 2010, 25 (1), 17-24. (14) Mayer, M. T.; Du, C.; Wang, D. J. Am. Chem. Soc. 2012, 134 296
- 297 (30), 12406-12409. (15) Siegbahn, P. E. M.; Crabtree, R. H. J. Am. Chem. Soc. 1999, 121 298 299 (1), 117–127.
- (16) McEvoy, J. P.; Gascon, J. A.; Batista, V. S.; Brudvig, G. W. 300
- 301 Photochem. Photobiol. Sci. 2005, 4 (12), 940-949. (17) Tommos, C.; Tang, X.-S.; Warncke, K.; Hoganson, C. W.;
- 303 Styring, S.; McCracken, J.; Diner, B. A.; Babcock, G. T. J. Am. Chem. 304 Soc. 1995, 117 (41), 10325-10335.
- (18) Yamaguchi, K.; Yamanaka, S.; Isobe, H.; Tanaka, K.; Ueyama, N. 305 306 Int. J. Quantum Chem. 2012, 112, 3849-3866.
- 307 (19) Bozoglian, F.; Romain, S.; Ertem, M. Z.; Todorova, T. K.; Sens,
- 308 C.; Mola, J.; Rodríguez, M.; Romero, I.; Benet-Buchholz, J.;
- 309 Fontrodona, X.; Cramer, C. J.; Gagliardi, L.; Llobet, A. J. Am. Chem. 310 Soc. 2009, 131 (42), 15176-15187.
- (20) Mavros, M. G.; Tsuchimochi, T.; Kowalczyk, T.; McIsaac, A.;
- 312 Wang, L.-P.; Van Voorhis, T. Inorg. Chem. 2014, 53 (13), 6386-6397.
- (21) Chrétien, S.; Metiu, H. J. Chem. Phys. 2008, 129 (7), 74705. 313
- (22) Torun, E.; Fang, C. M.; de Wijs, G. A.; de Groot, R. A. J. Phys. 314 315 Chem. C 2013, 117 (12), 6353-6357.
- (23) Mtangi, W.; Kiran, V.; Fontanesi, C.; Naaman, R. J. Phys. Chem. 316 317 Lett. 2015, 6 (24), 4916-4922.
- 318 (24) Annu. Rev. Phys. Chem. 2015, 66 (1), 263-281.
- (25) Klein, J. H.; Schmidt, D.; Steiner, U. E.; Lambert, C. J. Am. 320 Chem. Soc. 2015, 137 (34), 11011-11021.
- 321 (26) Helmich, F.; Lee, C. C.; Nieuwenhuizen, M. M. L.; Gielen, J. C.;
- Christianen, P. C. M.; Larsen, A.; Fytas, G.; Leclère, P. E. L. G.;
- 323 Schenning, A. P. H. J.; Meijer, E. W. Angew. Chem., Int. Ed. 2010, 49, 324 3939-3942.
- (27) Helmich, F.; Lee, C. C.; Schenning, A. P. H. J.; Meijer, E. W. J. 325 326 Am. Chem. Soc. 2010, 132 (47), 16753-16755.
- 327 (28) Kiran, V.; Mathew, S. P.; Cohen, S. R.; Hernández Delgado, I.;
- 328 Lacour, J.; Naaman, R. Adv. Mater. 2016, 28, 1957-1962. (29) Xie, Z.; Markus, T. Z.; Cohen, S. R.; Vager, Z.; Gutierrez, R.; 329
- 330 Naaman, R. Nano Lett. 2011, 11 (11), 4652-4655.
- 331 (30) Moore, G. F.; Blakemore, J. D.; Milot, R. L.; Hull, J. F.; Song,
- 332 H.; Cai, L.; Schmuttenmaer, C. A.; Crabtree, R. H.; Brudvig, G. W.
- 333 Energy Environ. Sci. 2011, 4 (7), 2389-2392.
- (31) Li, Z.; Kong, C.; Lu, G. J. Phys. Chem. C 2016, 120 (1), 56-63. 334
- (32) Gu, B.; Kiwi, J.; Graetzel, M. In Hydrogen Systems; Pergamon, 335 336 1986; Vol. 1, pp 121-134.
- (33) Hansen, W. N.; Kuwana, T.; Osteryoung, R. A. Anal. Chem. 337 338 **1966**, 38 (13), 1810–1821.
- (34) Linsebigler, A. L.; Lu, G.; Yates, J. T. Chem. Rev. 1995, 95 (3), 339 340 735-758.
- (35) Rossmeisl, J.; Qu, Z.-W.; Zhu, H.; Kroes, G.-J.; Nørskov, J. K. J. 341
- 342 Electroanal. Chem. 2007, 607 (1-2), 83-89.
- (36) Jirkovský, J.; Makarova, M.; Krtil, P. Electrochem. Commun.
- 344 **2006**, 8 (9), 1417–1422.